



ENDÜSTRİDE MALZEME SEÇİMİ

Doç.Dr. İrfan AY / Arş.Gör. T.Kerem DEMİRCİOĞLU

Prof. Dr. İrfan AY



Doç. Dr. İRFAN AY / Arş. Gör. T.KEREM DEMİRCİOĞLU



MALZEME SEÇİMİ İÇİN TABLOLAR

Doç.Dr. İrfan Ay / Arş. Gör. T.KEREM DEMİRCİOĞLU



BALIKESİR



ÜNİVERSİTESİ



Doç. Dr. İRFAN AY / Arş. Gör. T.KEREM DEMİRCİOĞLU



FİZİKSEL SABİTLER



PHYSICAL CONSTANTS IN SI UNITS

Absolute zero of temperature	- 273.15 °C
Acceleration due to gravity, g	9.807 m/s ²
Avogadro's number, N_A	6.022x10 ²⁶ /kmol
Base of natural logarithms, e	2.718
Boltzmann's constant, k	1.381 x 10 ⁻²⁶ kJ/K
Faraday's constant, F	9.648 x 10 ⁷ C/kmol
Universal Gas constant, \bar{R}	8.3143 kJ/kmol K
Permeability of vacuum, μ_0	1.257 x 10 ⁻⁶ H/m
Permittivity of vacuum, ϵ_0	8.854 x 10 ⁻¹² F/m
Planck's constant, h	6.626 x 10 ⁻³⁷ kJ/s
Velocity of light in vacuum, c	2.998 x 10 ⁸ m/s
Volume of perfect gas at STP	22.41 m ³ /kmol





BİRİMLERİN DÖNÜŞÜMÜ



Angle, θ	1 rad	57.30 °
Energy, U	See inside back cover	
Force, F	1 kgf 1 lbf	9.807 N 4.448 N
Length, l	1 ft 1 inch 1 Å	304.8 mm 25.40 mm 0.1 nm
Mass, M	1 tonne 1 lb	1000 kg 0.454 kg
Power, P	See inside back cover	
Stress, σ	See inside back cover	
Specific Heat, C_p	1 cal/g.°C	4.188 kJ/kg.K
Stress Intensity, K	1 ksi $\sqrt{\text{in}}$	1.10 MPa $\sqrt{\text{m}}$
Temperature, T	1 °F	0.556 K
Thermal Conductivity, λ	1 cal/s.cm.°C	4.18 W/m.K
Volume, V	1 Imperial gall 1 US gall	4.546 x 10 ⁻³ m ³ 3.785 x 10 ⁻³ m ³
Viscosity, η	1 poise 1 lb ft.s	0.1 N.s/m ² 0.1517 N.s/m ²





FORMÜL VE TANIMLAR

STRESS AND STRAIN

$$\sigma_t = \frac{F}{A}$$

$$\sigma_n = \frac{F}{A_o}$$

$$\varepsilon_t = \ln\left(\frac{\ell}{\ell_o}\right)$$

$$\varepsilon_n = \frac{\ell - \ell_o}{\ell_o}$$

F = normal component of force

A_o = initial area

A = current area

ℓ_o = initial length

ℓ = current length

σ_t = true stress

σ_n = nominal stress

ε_t = true strain

ε_n = nominal strain





FORMÜL VE TANIMLAR -2



Poisson's ratio, $\nu = - \frac{\text{lateral strain}}{\text{longitudinal strain}}$

Young's modulus $E =$ initial slope of $\sigma_t - \varepsilon_t$ curve = initial slope of $\sigma_n - \varepsilon_n$ curve.

Yield stress σ_y is the nominal stress at the limit of elasticity in a tensile test.

Tensile strength σ_{ts} is the nominal stress at maximum load in a tensile test.

Tensile ductility ε_f is the nominal plastic strain at failure in a tensile test. The gauge length of the specimen should also be quoted.





FORMÜL VE TANIMLAR -3



ELASTIC MODULI

$$G = \frac{E}{2(1 + \nu)} \quad K = \frac{E}{3(1 - 2\nu)}$$

For polycrystalline solids, as a rough guide,

Poisson's Ratio $\nu \approx \frac{1}{3}$

Shear Modulus $G \approx \frac{3}{8} E$

Bulk Modulus $K \approx E$


These approximations break down for rubber and porous solids.





FORMÜL VE TANIMLAR -3

(Tek yönlü Kompozitler için rijitlik ve mukavemet)



$$E_{II} = V_f E_f + (1 - V_f) E_m$$

$$E_{\perp} = \left(\frac{V_f}{E_f} + \frac{1-V_f}{E_m} \right)^{-1}$$

$$\sigma_{ts} = V_f \sigma_f^f + (1 - V_f) \sigma_y^m$$

E_{II} = composite modulus parallel to fibres (upper bound)

E_{\perp} = composite modulus transverse to fibres (lower bound)

V_f = volume fraction of fibres

E_f = Young's modulus of fibres

E_m = Young's modulus of matrix

σ_{ts} = tensile strength of composite parallel to fibres

σ_f^f = fracture strength of fibres

σ_y^m = yield stress of matrix





FORMÜL VE TANIMLAR -3 (Dislokasyonlar ve plastik akma)

DISLOCATIONS AND PLASTIC FLOW

The force per unit length F on a dislocation, of Burger's vector b , due to a remote shear stress τ , is $F = \tau b$. The shear stress τ_y required to move a dislocation on a single slip plane is

$$\tau_y = \frac{cT}{bL} \quad \text{where } T = \text{line tension (about } \frac{1}{2}Gb^2, \text{ where } G \text{ is the shear modulus)}$$

L = inter-obstacle distance

c = constant ($c \approx 2$ for strong obstacles, $c < 2$ for weak obstacles)

The **shear yield stress** k of a **polycrystalline solid** is related to the shear stress τ_y required to move a dislocation on a single slip plane: $k \approx \frac{3}{2}\tau_y$.

The **uniaxial yield stress** σ_y of a **polycrystalline solid** is approximately $\sigma_y = 2k$, where k is the shear yield stress.

Hardness H (in MPa) is given approximately by: $H \approx 3\sigma_y$.

Vickers Hardness HV is given in kgf/mm^2 , i.e. $HV = H/g$, where g is the acceleration due to gravity.





FORMÜL VE TANIMLAR -3 (Gevrek kırılma)

FAST FRACTURE

The stress intensity factor, K :
$$K = Y \sigma \sqrt{\pi a}$$

Fast fracture occurs when $K = K_{IC}$

In plane strain, the relationship between stress intensity factor K and strain energy release rate G is:

$$K = \sqrt{\frac{EG}{1-\nu^2}} \approx \sqrt{EG} \quad (\text{as } \nu^2 \approx 0.1)$$

Plane strain fracture toughness and toughness are thus related by:
$$K_{IC} = \sqrt{\frac{E G_{IC}}{1-\nu^2}} \approx \sqrt{E G_{IC}}$$

“Process zone size” at crack tip given approximately by:
$$r_p = \frac{K_{IC}^2}{\pi \sigma_f^2}$$

Note that K_{IC} (and G_{IC}) are only valid when conditions for linear elastic fracture mechanics apply (typically the crack length and specimen dimensions must be at least 50 times the process zone size).





FORMÜL VE TANIMLAR -3 (Gevrek kırılma -2)

In the above:

σ = remote tensile stress

a = crack length

Y = dimensionless constant dependent on geometry; typically $Y \approx 1$

K_{IC} = plane strain fracture toughness;

G_{IC} = critical strain energy release rate, or toughness;

E = Young's modulus

ν = Poisson's ratio

σ_f = failure strength





FORMÜL VE TANIMLAR -3 (Kırılma İstatistiği)



STATISTICS OF FRACTURE

$$\text{Weibull distribution, } P_s(V) = \exp \left\{ \int_V - \left(\frac{\sigma}{\sigma_o} \right)^m \frac{dV}{V_o} \right\}$$

$$\text{For constant stress: } P_s(V) = \exp \left\{ - \left(\frac{\sigma}{\sigma_o} \right)^m \frac{V}{V_o} \right\}$$

P_s = survival probability of component

V = volume of component

σ = tensile stress on component

V_o = volume of test sample

σ_o = reference failure stress for volume V_o , which gives $P_s = \frac{1}{e} = 0.37$

m = Weibull modulus





FORMÜL VE TANIMLAR -3 (Yorulma)

FATIGUE

Basquin's Law (high cycle fatigue):

$$\Delta\sigma N_f^\alpha = C_1$$

Coffin-Manson Law (low cycle fatigue):

$$\Delta\varepsilon^{pl} N_f^\beta = C_2$$

Goodman's Rule. For the same fatigue life, a stress range $\Delta\sigma$ operating with a mean stress σ_m , is equivalent to a stress range $\Delta\sigma_o$ and zero mean stress, according to the relationship:

$$\Delta\sigma = \Delta\sigma_o \left(1 - \frac{\sigma_m}{\sigma_{ts}}\right)$$

Miner's Rule for cumulative damage (for i loading blocks, each of constant stress amplitude and duration N_i cycles):

$$\sum_i \frac{N_i}{N_{fi}} = 1$$

Paris' crack growth law:

$$\frac{da}{dN} = A \Delta K^n$$





FORMÜL VE TANIMLAR -3 (Yorulma-2)

In the above:

$\Delta\sigma$ = stress range;

$\Delta\varepsilon^{pl}$ = plastic strain range;

ΔK = tensile stress intensity range;

N = cycles;

N_f = cycles to failure;

$\alpha, \beta, C_1, C_2, A, n$ = constants;

a = crack length;

σ_{ts} = tensile strength.





FORMÜL VE TANIMLAR -3 (Sürünme)

CREEP

Power law creep: $\dot{\epsilon}_{ss} = A \sigma^n \exp(-Q/RT)$

$\dot{\epsilon}_{ss}$ = steady-state strain-rate


Q = activation energy (kJ/kmol)

R = universal gas constant

T = absolute temperature

A, n = constants





FORMÜL VE TANIMLAR -3 (Difüzyon)

DIFFUSION

Diffusion coefficient: $D = D_o \exp(-Q / RT)$

Fick's diffusion equations: $J = -D \frac{dC}{dx}$ and $\frac{\partial C}{\partial t} = D \frac{\partial^2 C}{\partial x^2}$

C = concentration

x = distance

t = time

J = diffusive flux

D = diffusion coefficient (m^2/s)

D_o = pre-exponential factor (m^2/s)

Q = activation energy (kJ/kmol)





FORMÜL VE TANIMLAR -3 (Isı Akışı)



HEAT FLOW

Steady-state 1D heat flow (Fourier's Law): $q = -\lambda \frac{dT}{dx}$

Transient 1D heat flow: $\frac{\partial T}{\partial t} = a \frac{\partial^2 T}{\partial x^2}$

T = temperature (K)

λ = thermal conductivity (W/m.K)

q = heat flux per second, per unit area (W/m².s)

a = thermal diffusivity (m²/s)

For many 1D problems of diffusion and heat flow, the solution for concentration or temperature depends on the error function, erf :

$$C(x,t) = f \left[\operatorname{erf} \left(\frac{x}{2\sqrt{Dt}} \right) \right] \quad \text{or} \quad T(x,t) = f \left[\operatorname{erf} \left(\frac{x}{2\sqrt{at}} \right) \right]$$

A characteristic diffusion distance in all problems is given by $x \approx \sqrt{Dt}$, with the corresponding characteristic heat flow distance in thermal problems being $x \approx \sqrt{at}$.

The error function, and its first derivative, are:

$$\operatorname{erf}(X) = \frac{2}{\sqrt{\pi}} \int_0^X \exp(-y^2) dy \quad \text{and} \quad \frac{d}{dX} [\operatorname{erf}(X)] = \frac{2}{\sqrt{\pi}} \exp(-X^2)$$





FORMÜL VE TANIMLAR -3 (Isı Akışı-2)

The error function integral has no closed form solution – values are given in the Table below.

X	0	0.1	0.2	0.3	0.4	0.5	0.6	0.7	0.8
$erf(X)$	0	0.11	0.22	0.33	0.43	0.52	0.60	0.68	0.74

X	0.9	1.0	1.1	1.2	1.3	1.4	1.5	∞
$erf(X)$	0.80	0.84	0.88	0.91	0.93	0.95	0.97	1.0





MALZEMELERİN FİZİKSEL VE MEKANİK ÖZELLİKLERİ

II. PHYSICAL AND MECHANICAL PROPERTIES OF MATERIALS

II.1 MELTING (or SOFTENING) TEMPERATURE, T_m

All data are for melting points at atmospheric pressure. For polymers (and glasses) the data indicate the glass transition (softening) temperature, above which the mechanical properties rapidly fall. Melting temperatures of selected elements are given in section VIII.

		T_m (°C)	
Metals	Ferrous	Cast Irons	1130 - 1250
		High Carbon Steels	1289 - 1478
		Medium Carbon Steels	1380 - 1514
		Low Carbon Steels	1480 - 1528
		Low Alloy Steels	1382 - 1529
	Non-ferrous	Stainless Steels	1375 - 1450
		Aluminium Alloys	475 - 677
		Copper Alloys	982 - 1082
		Lead Alloys	322 - 328
		Magnesium Alloys	447 - 649
		Nickel Alloys	1435 - 1486
		Titanium Alloys	1477 - 1682
		Zinc Alloys	375 - 492
		Ceramics	Glasses
Glass Ceramic (*)	563 - 1647		
Silica Glass (*)	957 - 1557		
Soda-Lime Glass (*)	442 - 592		
Brick	927 - 1227		
Porous	Concrete, typical		927 - 1227
	Stone		1227 - 1427
Technical	Alumina		2004 - 2096
	Aluminium Nitride		2397 - 2507
	Boron Carbide		2372 - 2507
	Silicon		1407 - 1412
	Silicon Carbide		2152 - 2500
	Silicon Nitride		2388 - 2496
	Tungsten Carbide		2827 - 2920
Composites	Metal Polymer	Aluminium/Silicon Carbide	525 - 627
		CFRP	n/a
	GFRP	n/a	
Natural	Bamboo (*)	77 - 102	
	Cork (*)	77 - 102	
	Leather (*)	107 - 127	
	Wood, typical (Longitudinal) (*)	77 - 102	
	Wood, typical (Transverse) (*)	77 - 102	

		T_m (°C)		
Polymers ¹	Elastomer	Butyl Rubber (*)	-73 - -63	
		EVA (*)	-73 - -23	
		Isoprene (IR) (*)	-83 - -78	
		Natural Rubber (NR) (*)	-78 - -63	
		Neoprene (CR) (*)	-48 - -43	
		Polyurethane Elastomers (elPU) (*)	-73 - -23	
	Thermoplastic	Silicone Elastomers (*)	-123 - -73	
		ABS (*)	88 - 128	
		Cellulose Polymers (CA) (*)	-9 - 107	
		Ionomer (I) (*)	27 - 77	
		Nylons (PA) (*)	44 - 56	
		Polycarbonate (PC) (*)	142 - 205	
		PEEK (*)	143 - 199	
		Polyethylene (PE) (*)	-25 - -15	
		PET (*)	68 - 80	
		Acrylic (PMMA) (*)	85 - 165	
		Acetal (POM) (*)	-18 - -8	
		Polypropylene (PP) (*)	-25 - -15	
		Polystyrene (PS) (*)	74 - 110	
		Polyurethane Thermoplastics (tpPU) (*)	120 - 180	
		PVC	75 - 105	
		Teflon (PTFE)	107 - 123	
		Thermoset	Epoxies	n/a
			Phenolics	n/a
Polyester	n/a			
Polymer Foams				
Polymer Foams	Flexible Polymer Foam (VLD) (*)	112 - 177		
	Flexible Polymer Foam (LD) (*)	112 - 177		
	Flexible Polymer Foam (MD) (*)	112 - 177		
	Rigid Polymer Foam (LD) (*)	67 - 171		
	Rigid Polymer Foam (MD) (*)	67 - 157		
	Rigid Polymer Foam (HD) (*)	67 - 171		

¹ For full names and acronyms of polymers – see Section V.
 (*) glass transition (softening) temperature
 n/a: not applicable (materials decompose, rather than melt)
 (Data courtesy of Granta Design Ltd)



MALZEMELERİN YOĞUNLUKLARI

II.2 DENSITY, ρ

		ρ (Mg/m ³)	
Metals	Ferrous	Cast Irons	7.05 - 7.25
		High Carbon Steels	7.8 - 7.9
		Medium Carbon Steels	7.8 - 7.9
		Low Carbon Steels	7.8 - 7.9
		Low Alloy Steels	7.8 - 7.9
	Non-ferrous	Stainless Steels	7.8 - 8.1
		Aluminium Alloys	2.5 - 2.9
		Copper Alloys	8.93 - 8.94
		Lead Alloys	10 - 11.4
		Magnesium Alloys	1.74 - 1.95
		Nickel Alloys	8.83 - 8.95
		Titanium Alloys	4.4 - 4.8
		Zinc Alloys	4.95 - 7
		Ceramics	Glasses
Glass Ceramic	2.2 - 2.8		
Silica Glass	2.17 - 2.22		
Soda-Lime Glass	2.44 - 2.49		
Porous	Brick		1.9 - 2.1
	Concrete, typical		2.2 - 2.6
	Stone		2.5 - 3
Technical	Alumina		3.5 - 3.98
	Aluminium Nitride		3.26 - 3.33
	Boron Carbide		2.35 - 2.55
	Silicon		2.3 - 2.35
	Silicon Carbide		3 - 3.21
	Silicon Nitride		3 - 3.29
	Tungsten Carbide		15.3 - 15.9
Composites	Metal Polymer	Aluminium/Silicon Carbide	2.86 - 2.9
		CFRP	1.5 - 1.8
		GFRP	1.75 - 1.97
		Natural	Bamboo
Cork	0.12 - 0.24		
Leather	0.81 - 1.05		
Wood, typical (Longitudinal)	0.6 - 0.8		
Wood, typical (Transverse)	0.6 - 0.8		

		ρ (Mg/m ³)		
Polymers¹	Elastomer	Butyl Rubber	0.9 - 0.92	
		EVA	0.945 - 0.955	
		Isoprene (IR)	0.93 - 0.94	
		Natural Rubber (NR)	0.92 - 0.93	
		Neoprene (CR)	1.23 - 1.25	
		Polyurethane Elastomers (ePU)	1.02 - 1.25	
		Silicone Elastomers	1.3 - 1.8	
		Thermoplastic	ABS	1.01 - 1.21
			Cellulose Polymers (CA)	0.98 - 1.3
			Ionomer (I)	0.93 - 0.98
	Nylons (PA)		1.12 - 1.14	
	Polycarbonate (PC)		1.14 - 1.21	
	PEEK		1.3 - 1.32	
	Polyethylene (PE)		0.939 - 0.98	
	PET		1.29 - 1.4	
	Acrylic (PMMA)		1.18 - 1.22	
	Acetal (POM)		1.39 - 1.43	
	Polypropylene (PP)		0.89 - 0.91	
	Polystyrene (PS)		1.04 - 1.05	
	Thermoset	Polyurethane Thermoplastics (tpPU)	1.12 - 1.24	
		PVC	1.3 - 1.58	
		Teflon (PTFE)	2.14 - 2.2	
		Epoxies	1.11 - 1.4	
		Phenolics	1.24 - 1.32	
	Polymer Foams	Polyester	1.04 - 1.4	
		Flexible Polymer Foam (VLD)	0.016 - 0.035	
		Flexible Polymer Foam (LD)	0.038 - 0.07	
Flexible Polymer Foam (MD)		0.07 - 0.115		
Rigid Polymer Foam (LD)		0.036 - 0.07		
Rigid Polymer Foam (MD)		0.078 - 0.165		
Rigid Polymer Foam (HD)	0.17 - 0.47			

¹ For full names and acronyms of polymers – see Section V (Data courtesy of Granta Design Ltd).

MALZEMELERİN YOUNG MODÜLLERİ

II.3 YOUNG'S MODULUS, E

		E (GPa)	
Metals	Ferrous	Cast Irons	165 - 180
		High Carbon Steels	200 - 215
		Medium Carbon Steels	200 - 216
		Low Carbon Steels	200 - 215
		Low Alloy Steels	201 - 217
		Stainless Steels	189 - 210
	Non-ferrous	Aluminium Alloys	68 - 82
		Copper Alloys	112 - 148
		Lead Alloys	12.5 - 15
		Magnesium Alloys	42 - 47
		Nickel Alloys	190 - 220
		Titanium Alloys	90 - 120
		Zinc Alloys	68 - 95
Ceramics	Glasses	Borosilicate Glass	61 - 64
		Glass Ceramic	64 - 110
		Silica Glass	68 - 74
		Soda-Lime Glass	68 - 72
	Porous	Brick	10 - 50
		Concrete, typical	25 - 38
		Stone	6.9 - 21
	Technical	Alumina	215 - 413
		Aluminium Nitride	302 - 348
		Boron Carbide	400 - 472
		Silicon	140 - 155
		Silicon Carbide	300 - 460
		Silicon Nitride	280 - 310
Tungsten Carbide	600 - 720		
Composites	Metal Polymer	Aluminium/Silicon Carbide	81 - 100
		CFRP	88 - 150
		GFRP	15 - 28
Natural	Bamboo	15 - 20	
	Cork	0.013 - 0.05	
	Leather	0.1 - 0.5	
	Wood, typical (Longitudinal)	8 - 20	
	Wood, typical (Transverse)	0.5 - 3	

		E (GPa)		
Polymers¹	Elastomer	Butyl Rubber	0.001 - 0.002	
		EVA	0.01 - 0.04	
		Isoprene (IR)	0.0014 - 0.004	
		Natural Rubber (NR)	0.0015 - 0.0025	
		Neoprene (CR)	0.0007 - 0.002	
		Polyurethane Elastomers (elPU)	0.002 - 0.003	
		Silicone Elastomers	0.005 - 0.02	
		Thermoplastic	ABS	1.1 - 2.9
			Cellulose Polymers (CA)	1.6 - 2
			Ionomer (I)	0.2 - 0.424
	Nylons (PA)		2.62 - 3.2	
	Polycarbonate (PC)		2 - 2.44	
	PEEK		3.5 - 4.2	
	Polyethylene (PE)		0.621 - 0.896	
	PET		2.76 - 4.14	
	Acrylic (PMMA)		2.24 - 3.8	
	Acetal (POM)		2.5 - 5	
	Polypropylene (PP)		0.896 - 1.55	
	Polystyrene (PS)		2.28 - 3.34	
	Polyurethane Thermoplastics (tpPU)		1.31 - 2.07	
	Thermoset	PVC	2.14 - 4.14	
		Teflon (PTFE)	0.4 - 0.562	
		Epoxies	2.35 - 3.075	
Phenolics		2.76 - 4.83		
Polymer Foams	Polyester	2.07 - 4.41		
	Flexible Polymer Foam (VLD)	0.0003 - 0.001		
	Flexible Polymer Foam (LD)	0.001 - 0.003		
	Flexible Polymer Foam (MD)	0.004 - 0.012		
	Rigid Polymer Foam (LD)	0.023 - 0.08		
	Rigid Polymer Foam (MD)	0.08 - 0.2		
Rigid Polymer Foam (HD)	0.2 - 0.48			

¹ For full names and acronyms of polymers – see Section V
(Data courtesy of Granta Design Ltd)



MALZEMELERİN AKMA VE MAX.ÇEKME MUKAVEMETLERİ



II.4 YIELD STRESS, σ_y , AND TENSILE STRENGTH, σ_{ts}

		σ_y (MPa)	σ_{ts} (MPa)	
Metals	Ferrous	Cast Irons	215 - 790	350 - 1000
		High Carbon Steels	400 - 1155	550 - 1640
		Medium Carbon Steels	305 - 900	410 - 1200
		Low Carbon Steels	250 - 395	345 - 580
		Low Alloy Steels	400 - 1100	460 - 1200
		Stainless Steels	170 - 1000	480 - 2240
		Aluminium Alloys	30 - 500	58 - 550
	Non-ferrous	Copper Alloys	30 - 500	100 - 550
		Lead Alloys	8 - 14	12 - 20
		Magnesium Alloys	70 - 400	185 - 475
		Nickel Alloys	70 - 1100	345 - 1200
		Titanium Alloys	250 - 1245	300 - 1625
		Zinc Alloys	80 - 450	135 - 520
		Ceramics	Glasses	Borosilicate Glass (*)
Glass Ceramic (*)	750 - 2129			62 - 177
Silica Glass (*)	1100 - 1600			45 - 155
Soda-Lime Glass (*)	360 - 420			31 - 35
Porous	Brick (*)		50 - 140	7 - 14
	Concrete, typical (*)		32 - 60	2 - 6
	Stone (*)		34 - 248	5 - 17
Technical	Alumina (*)		690 - 5500	350 - 665
	Aluminium Nitride (*)		1970 - 2700	197 - 270
	Boron Carbide (*)		2583 - 5687	350 - 560
	Silicon (*)		3200 - 3460	160 - 180
	Silicon Carbide (*)		1000 - 5250	370 - 660
	Silicon Nitride (*)		524 - 5500	690 - 800
	Tungsten Carbide (*)		3347 - 6833	370 - 550
Composites	Metal Polymer	Aluminium/Silicon Carbide	280 - 324	290 - 385
		CFRP	550 - 1050	550 - 1050
		GFRP	110 - 192	138 - 241
Natural	Bamboo	35 - 44	36 - 45	
	Cork	0.3 - 1.5	0.5 - 2.5	
	Leather	5 - 10	20 - 26	
	Wood, typical (Longitudinal)	30 - 70	60 - 100	
	Wood, typical (Transverse)	2 - 6	4 - 9	

(Data courtesy of Granta Design Ltd)

		σ_y (MPa)	σ_{ts} (MPa)	
Polymers ¹	Elastomer	Butyl Rubber	2 - 3	5 - 10
		EVA	12 - 18	16 - 20
		Isoprene (IR)	20 - 25	20 - 25
		Natural Rubber (NR)	20 - 30	22 - 32
		Neoprene (CR)	3.4 - 24	3.4 - 24
		Polyurethane Elastomers (elPU)	25 - 51	25 - 51
		Silicone Elastomers	2.4 - 5.5	2.4 - 5.5
	Thermoplastic	ABS	18.5 - 51	27.6 - 55.2
		Cellulose Polymers (CA)	25 - 45	25 - 50
		Ionomer (I)	8.3 - 15.9	17.2 - 37.2
		Nylons (PA)	50 - 94.8	90 - 165
		Polycarbonate (PC)	59 - 70	60 - 72.4
		PEEK	65 - 95	70 - 103
		Polyethylene (PE)	17.9 - 29	20.7 - 44.8
PET		56.5 - 62.3	48.3 - 72.4	
Acrylic (PMMA)		53.8 - 72.4	48.3 - 79.6	
Acetal (POM)		48.6 - 72.4	60 - 89.6	
Thermoset	Polypropylene (PP)	20.7 - 37.2	27.6 - 41.4	
	Polystyrene (PS)	28.7 - 56.2	36.9 - 56.5	
	Polyurethane Thermoplastics (tpPU)	40 - 53.8	31 - 62	
	PVC	35.4 - 52.1	40.7 - 65.1	
	Teflon (PTFE)	15 - 25	20 - 30	
	Epoxies	36 - 71.7	45 - 89.6	
	Phenolics	27.6 - 49.7	34.5 - 62.1	
	Polyester	33 - 40	41.4 - 89.6	
	Polymer Foams	Flexible Polymer Foam (VLD)	0.01 - 0.12	0.24 - 0.85
		Flexible Polymer Foam (LD)	0.02 - 0.3	0.24 - 2.35
Flexible Polymer Foam (MD)		0.05 - 0.7	0.43 - 2.95	
Rigid Polymer Foam (LD)		0.3 - 1.7	0.45 - 2.25	
Rigid Polymer Foam (MD)		0.4 - 3.5	0.65 - 5.1	
Rigid Polymer Foam (HD)	0.8 - 12	1.2 - 12.4		

¹ For full names and acronyms of polymers – see Section V.

(*) NB: For ceramics, yield stress is replaced by *compressive strength*, which is more relevant in ceramic design. Note that ceramics are of the order of 10 times stronger in compression than in tension.



MALZEMELERİN KIRILMA TOKLUĞU (K_{IC}) DEĞERLERİ

II.5 FRACTURE TOUGHNESS (PLANE STRAIN), K_{IC}

		K_{IC} (MPa√m)	
Metals	Ferrous	Cast Irons	22 - 54
		High Carbon Steels	27 - 92
		Medium Carbon Steels	12 - 92
		Low Carbon Steels	41 - 82
		Low Alloy Steels	14 - 200
	Non-ferrous	Stainless Steels	62 - 280
		Aluminium Alloys	22 - 35
		Copper Alloys	30 - 90
		Lead Alloys	5 - 15
		Magnesium Alloys	12 - 18
		Nickel Alloys	80 - 110
		Titanium Alloys	14 - 120
		Zinc Alloys	10 - 100
		Ceramics	Glasses
Glass Ceramic	1.4 - 1.7		
Silica Glass	0.6 - 0.8		
Soda-Lime Glass	0.55 - 0.7		
Porous	Brick		1 - 2
	Concrete, typical		0.35 - 0.45
Technical	Stone		0.7 - 1.5
	Alumina		3.3 - 4.8
	Aluminium Nitride		2.5 - 3.4
	Boron Carbide		2.5 - 3.5
	Silicon		0.83 - 0.94
	Silicon Carbide		2.5 - 5
Silicon Nitride	4 - 6		
Tungsten Carbide	2 - 3.8		
Composites	Metal Polymer	Aluminium/Silicon Carbide	15 - 24
		CFRP	6.1 - 88
	GFRP	7 - 23	
Natural	Bamboo	5 - 7	
	Cork	0.05 - 0.1	
	Leather	3 - 5	
	Wood, typical (Longitudinal)	5 - 9	
	Wood, typical (Transverse)	0.5 - 0.8	

(Data courtesy of Granta Design Ltd)

		K_{IC} (MPa√m)		
Polymers¹	Elastomer	Butyl Rubber	0.07 - 0.1	
		EVA	0.5 - 0.7	
		Isoprene (IR)	0.07 - 0.1	
		Natural Rubber (NR)	0.15 - 0.25	
		Neoprene (CR)	0.1 - 0.3	
		Polyurethane Elastomers (elPU)	0.2 - 0.4	
		Silicone Elastomers	0.03 - 0.5	
		Thermoplastic	ABS	1.19 - 4.30
			Cellulose Polymers (CA)	1 - 2.5
			Ionomer (I)	1.14 - 3.43
			Nylons (PA)	2.22 - 5.62
			Polycarbonate (PC)	2.1 - 4.60
	PEEK		2.73 - 4.30	
	Polyethylene (PE)		1.44 - 1.72	
	PET		4.5 - 5.5	
	Acrylic (PMMA)		0.7 - 1.6	
	Acetal (POM)		1.71 - 4.2	
	Polypropylene (PP)		3 - 4.5	
	Polystyrene (PS)		0.7 - 1.1	
	Thermoset	Polyurethane Thermoplastics (tpPU)	1.84 - 4.97	
		PVC	1.46 - 5.12	
		Teflon (PTFE)	1.32 - 1.8	
		Epoxies	0.4 - 2.22	
		Phenolics	0.79 - 1.21	
Polyester		1.09 - 1.70		
Polymer Foams		Flexible Polymer Foam (VLD)	0.005 - 0.02	
		Flexible Polymer Foam (LD)	0.015 - 0.05	
		Flexible Polymer Foam (MD)	0.03 - 0.09	
		Rigid Polymer Foam (LD)	0.002 - 0.02	
		Rigid Polymer Foam (MD)	0.007 - 0.049	
		Rigid Polymer Foam (HD)	0.024 - 0.091	

¹ For full names and acronyms of polymers – see Section V.

Note: K_{IC} only valid for conditions of linear elastic fracture mechanics (see I. Formulae & Definitions). Plane Strain Toughness, G_{IC} , may be estimated from $K_{IC}^2 = E G_{IC} / (1 - \nu^2) \approx E G_{IC}$ (as $\nu^2 \approx 0.1$).

MALZEMELERİN ÇEVRE DİRENCİ DEĞERLERİ

II.6 ENVIRONMENTAL RESISTANCE

		Flammability	Fresh water	Salt water	Sunlight (UV)	Wear resistance		
Metals	Ferrous	Cast Irons	A	B	C	A	A	
		High Carbon Steels	A	B	C	A	A	
		Medium Carbon Steels	A	B	C	A	A	
		Low Carbon Steels	A	B	C	A	A	
		Low Alloy Steels	A	B	C	A	A	
	Non-ferrous	Stainless Steels	A	A	A	A	B	
		Aluminium Alloys	B	A	B	A	C	
		Copper Alloys	A	A	A	A	A	
		Lead Alloys	A	A	A	A	C	
		Magnesium Alloys	A	A	D	A	C	
		Nickel Alloys	A	A	A	A	B	
		Titanium Alloys	A	A	A	A	A	
		Zinc Alloys	A	A	C	A	E	
		Ceramics	Glasses	Borosilicate Glass	A	B	B	A
Glass Ceramic	A			A	A	A	A	
Silica Glass	A			A	A	A	B	
Soda-Lime Glass	A			A	A	A	A	
Porous	Brick, Concrete, Stone		A	A	A	A	C	
	Technical		Alumina	A	A	A	A	A
Aluminium Nitride			A	A	A	A	A	
Boron Carbide			A	A	A	A	A	
Silicon			A	A	B	A	B	
Silicon Carbide			A	A	A	A	A	
Silicon Nitride			A	A	A	A	A	
Tungsten Carbide			A	A	A	A	A	
Composites			Metal Polymer	Aluminium/Silicon Carbide	A	A	B	A
	CFRP			B	A	A	B	C
	GFRP	B		A	A	B	C	
	Natural	Bamboo	D	C	C	B	D	
Cork	D	B	B	A	B			
Leather	D	B	B	B	B			
Wood	D	C	C	B	D			


		Flammability	Fresh water	Salt water	Sunlight (UV)	Wear resistance	
Polymers¹	Elastomer	Butyl Rubber	m	A	A	B	B
		EVA	m	A	A	B	B
		Isoprene (IR)	m	A	A	B	B
		Natural Rubber (NR)	m	A	A	B	B
		Neoprene (CR)	m	A	A	B	B
	Thermoplastic	Polyurethane Elastomers (ePU)	m	A	A	B	B
		Silicone Elastomers	b	A	A	B	B
		ABS	D	A	A	B	D
		Cellulose Polymers (CA)	D	A	A	B	C
		Ionomer (I)	D	A	A	B	C
		Nylons (PA)	C	A	A	B	C
		Polycarbonate (PC)	B	A	A	B	C
		PEEK	B	A	A	A	C
		Polyethylene (PE)	D	A	A	D	C
		PET	D	A	A	B	C
		Acrylic (PMMA)	D	A	A	A	C
		Acetal (POM)	D	A	A	C	B
		Polypropylene (PP)	D	A	A	D	C
		Polystyrene (PS)	D	A	A	C	D
		Polyurethane Thermoplastics (tpPU)	C	A	A	B	C
		PVC	A	A	A	A	C
		Thermoset	Teflon (PTFE)	A	A	A	B
Epoxies	B		A	A	B	C	
Phenolics	B		A	A	A	C	
Polyester	D		A	A	A	C	
Polymer Foams	Flexible Polymer Foams	E	A	A	C	D	
	Rigid Polymer Foams	C	A	A	B	E	

¹ For full names and acronyms of polymers – see Section V.

Ranking:

A = very good; B = good; C = average; D = poor; E = very poor.

(Data courtesy of Granta Design Ltd)



SEÇİLMİŞ METAL VE POLİMERLERİN TEK EKSENLİ ÇEKME EĞRİ DEĞERLERİ

II.7 UNIAXIAL TENSILE RESPONSE OF SELECTED METALS & POLYMERS

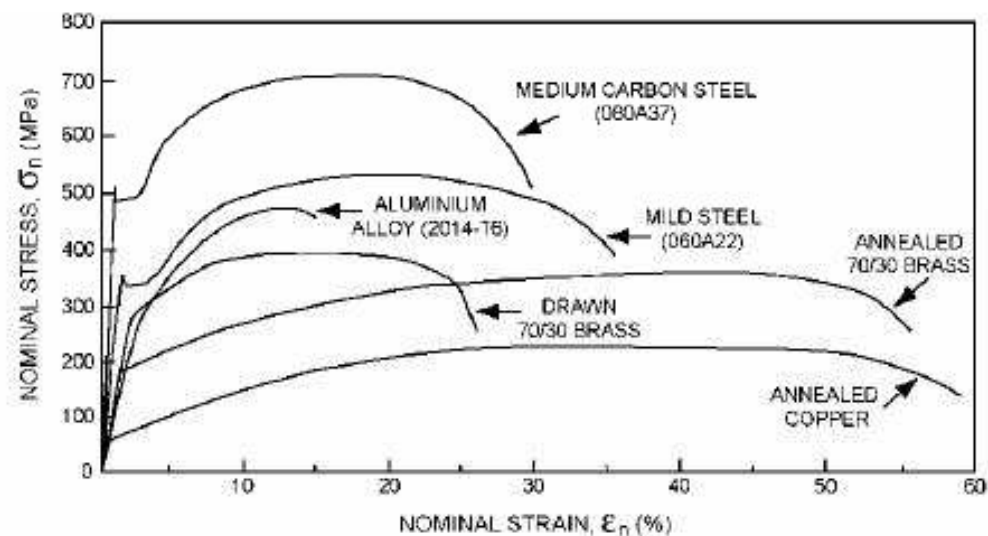


Figure 2.1 Tensile response of some common metals






BALIKESİR ÜNİVERSİTESİ
1992


SEÇİLMİŞ METAL VE POLİMERLERİN TEK EKSENLİ ÇEKME EĞRİ DEĞERLERİ-2

BALIKESİR ÜNİVERSİTESİ
1992

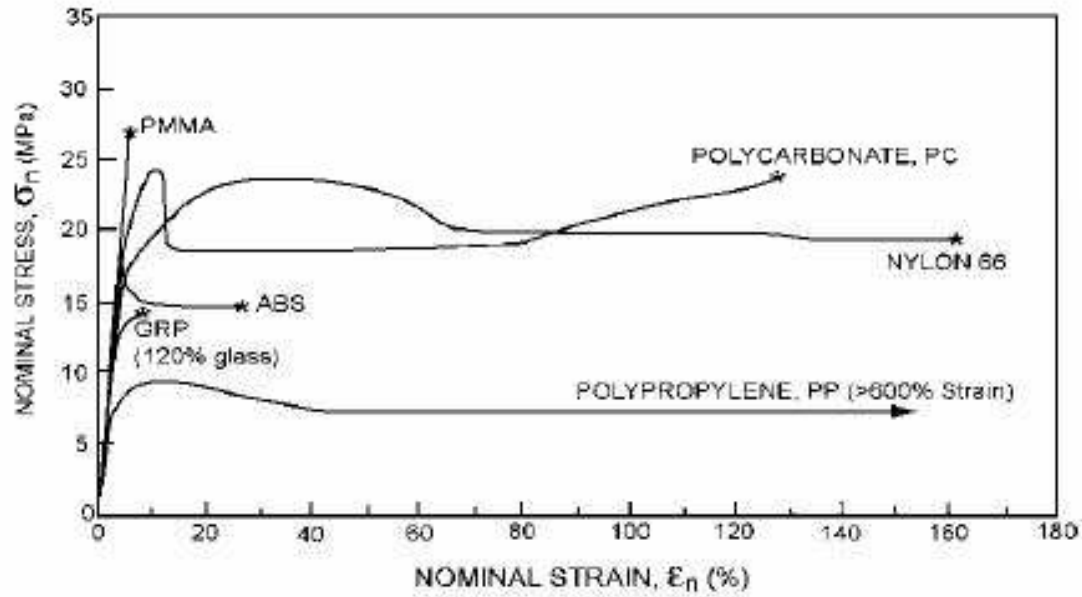




MALZEMELERİN MAX.İŞLETME SICAKLIKLARI

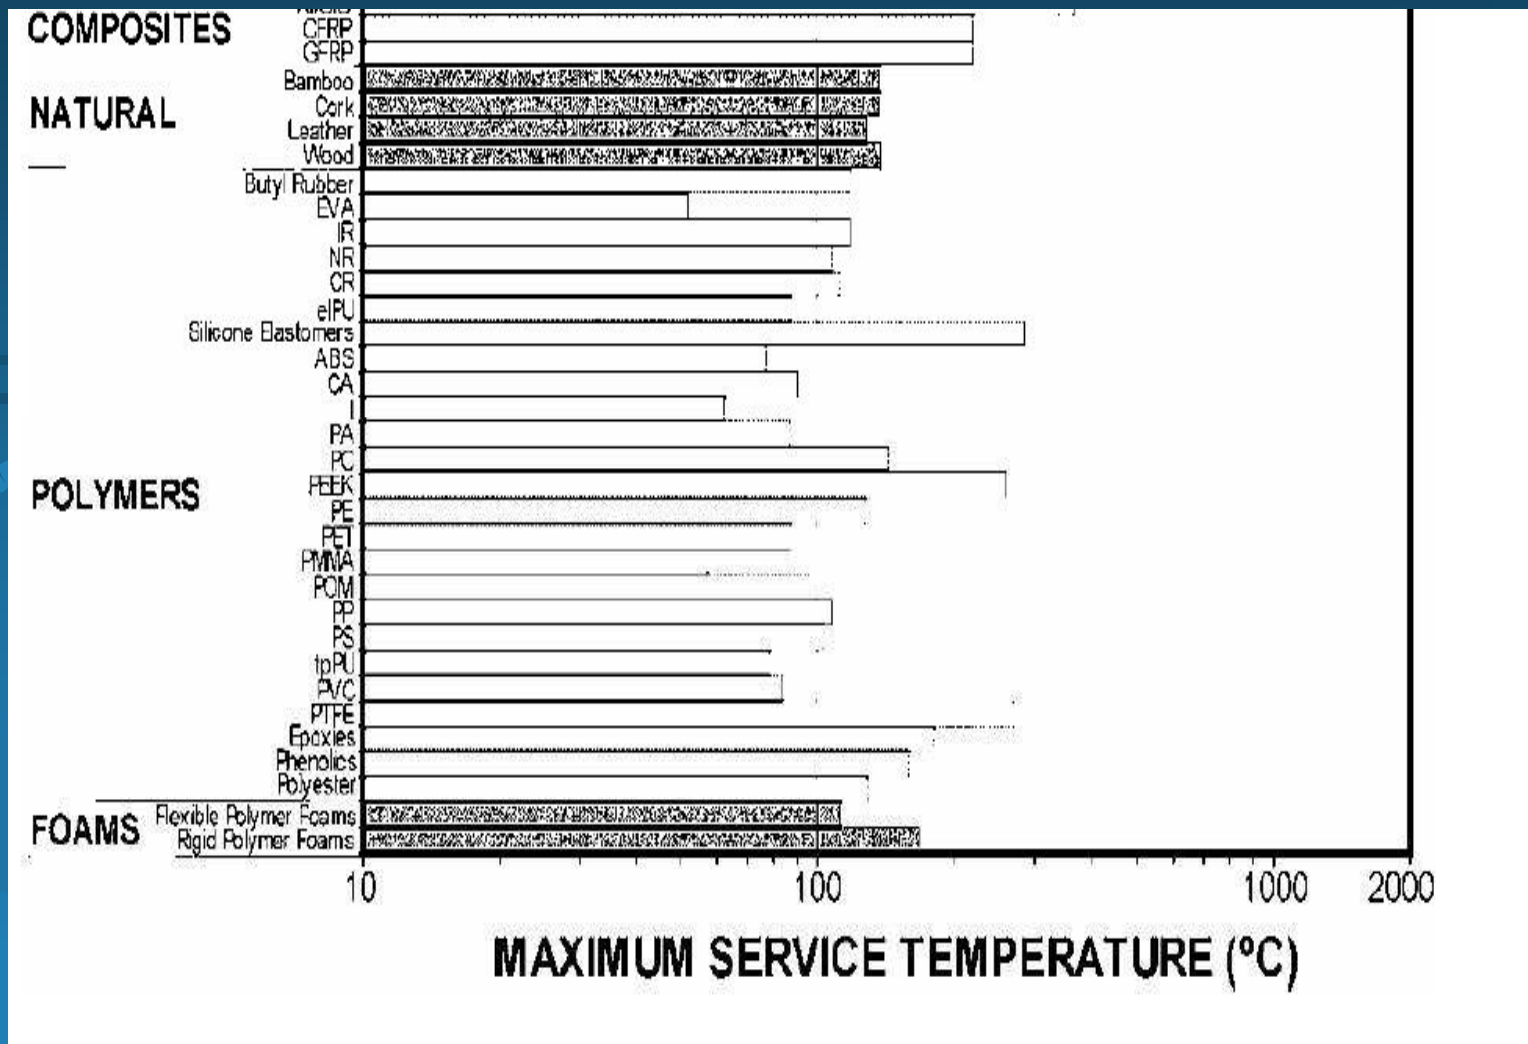



MALZEMELERİN MAX.İŞLETME SICAKLIKLARI

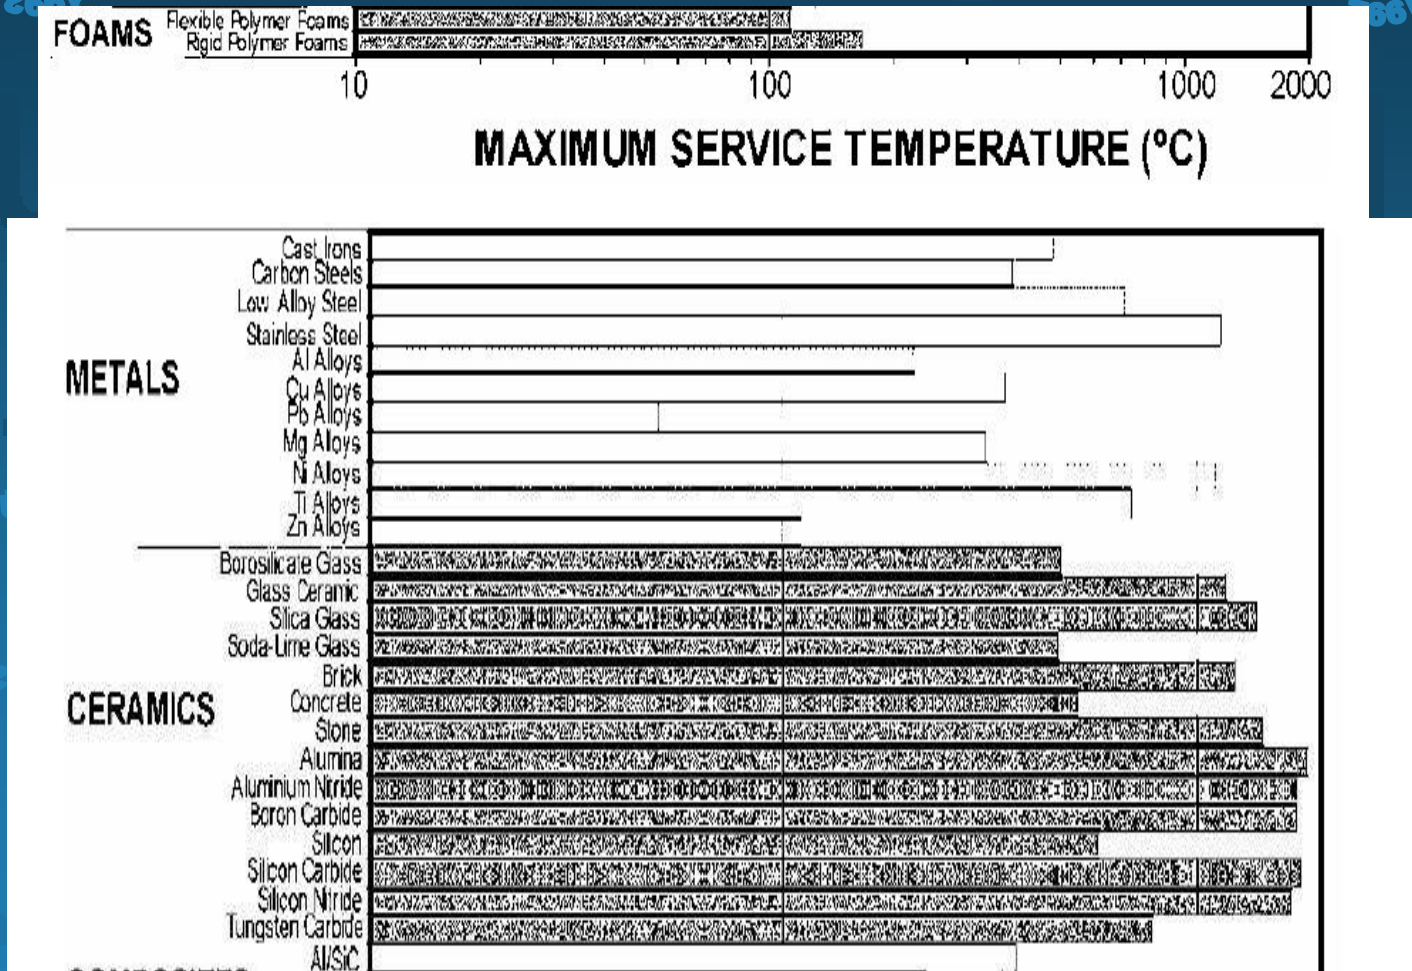




BALIKESİR ÜNİVERSİTESİ

BALIKESİR ÜNİVERSİTESİ

MALZEMELERİN FİYATLARI

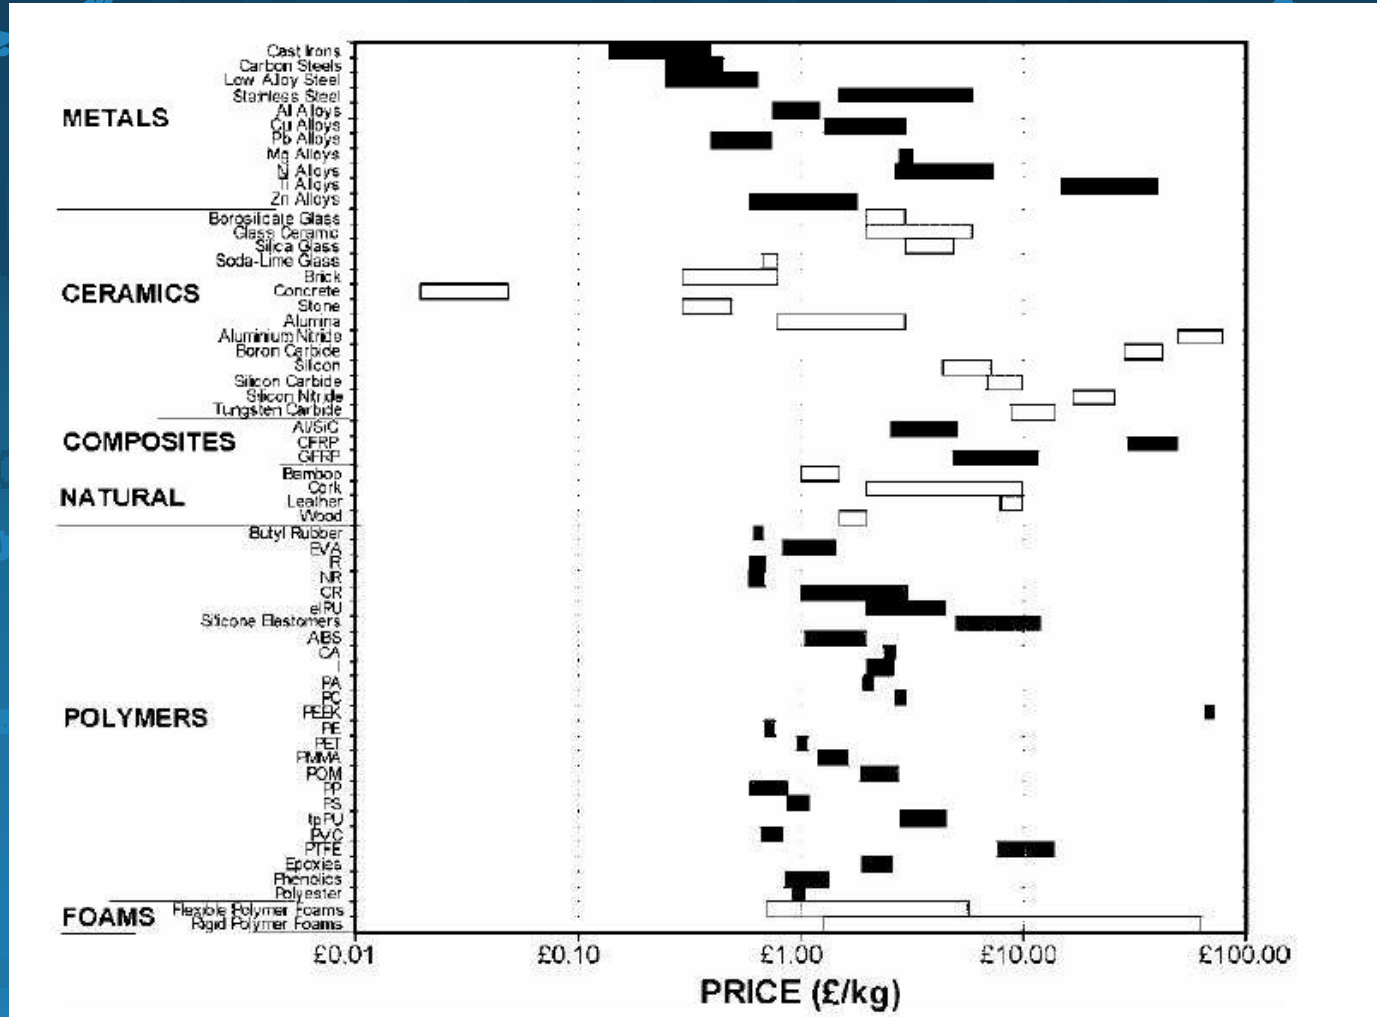

BALIKESİR ÜNİVERSİTESİ 1992



MALZEMELERİN PROSES ÖZELLİK KARTLARI

IV. PROCESS ATTRIBUTE CHARTS

IV.1 MATERIAL – PROCESS COMPATIBILITY MATRIX (SHAPING)

Figure 4.1a: Metals

Metals		Sand Casting	Die Casting	Investment Casting	Rolling/ Forging	Extrusion	Sheet Forming	Powder Methods	Machining
Ferrous	Cast Irons	•	•	•					
	Medium/High Carbon Steels	•		•	•			•	•
	Low Carbon Steels	•		•	•		•	•	•
	Low Alloy/Stainless Steels	•	•	•	•		•	•	•
Non-ferrous	Aluminium, Copper, Lead, Magnesium, Zinc Alloys	•	•	•	•	•	•	•	•
	Nickel Alloys	•	•	•	•		•	•	•
	Titanium Alloys		•		•	•	•	•	•

Figure 4.1b: Polymers and Foams

Polymers	Machining	Injection Moulding	Blow Moulding	Compression Moulding	Rotational Moulding	Polymer Casting	Composite Forming
Elastomers	•			•	•		
Thermoplastics	•	•	•	•	•		
Thermosets				•	•	•	•
Polymer Foams	•	•			•		

Notes on other materials:

Ceramics are all processed by powder methods, and Glasses are also moulded. Both are difficult to machine.

Polymer Composites are shaped by dedicated forming techniques, and are difficult to machine.


Natural Materials can only be machined, though some woods are also hot formed.

(Data courtesy of Granta Design Ltd)



MALZEMELERİN PROSES ÖZELLİK KARTLARI (Kütle)


IV.2 MASS

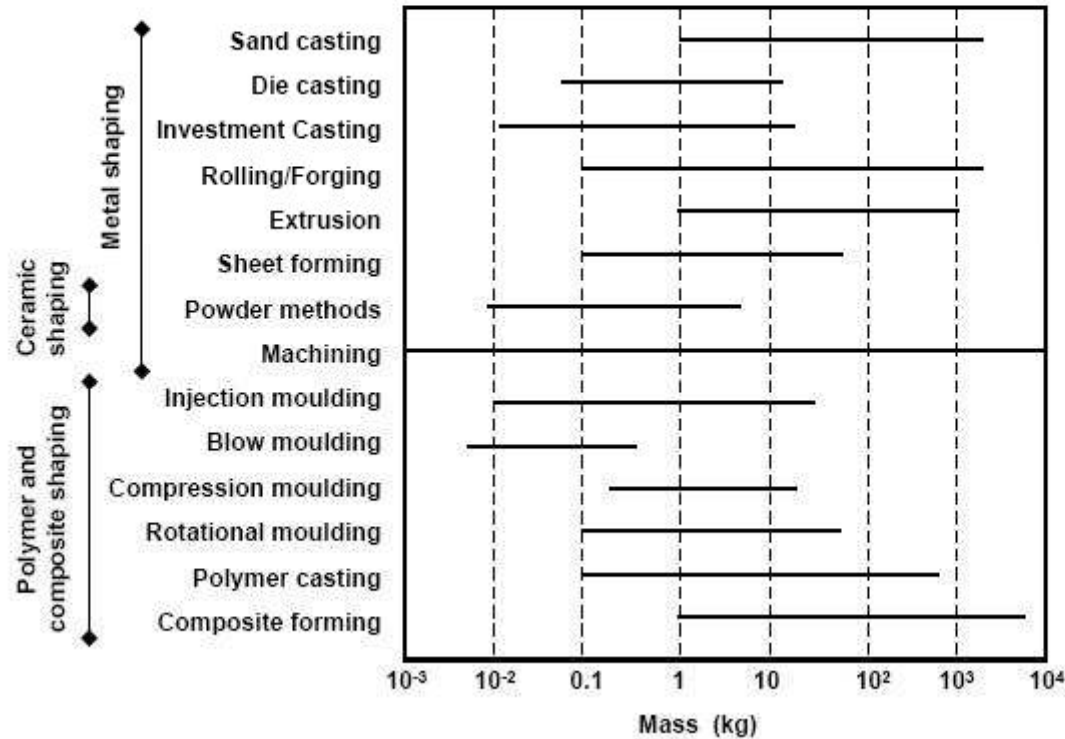



MALZEMELERİN PROSES ÖZELLİK KARTLARI (Kesit kalınlığı)


IV.3 SECTION THICKNESS

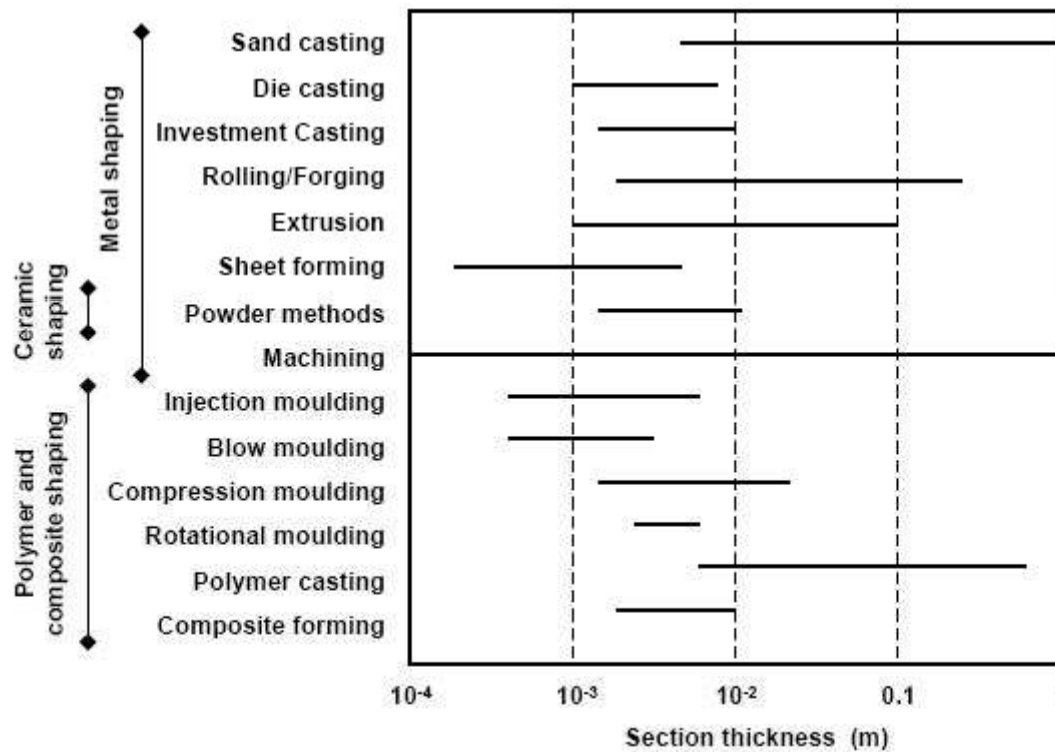




MALZEMELERİN PROSES ÖZELLİK KARTLARI (Yüzey pürüzlülüğü)


IV.4 SURFACE ROUGHNESS

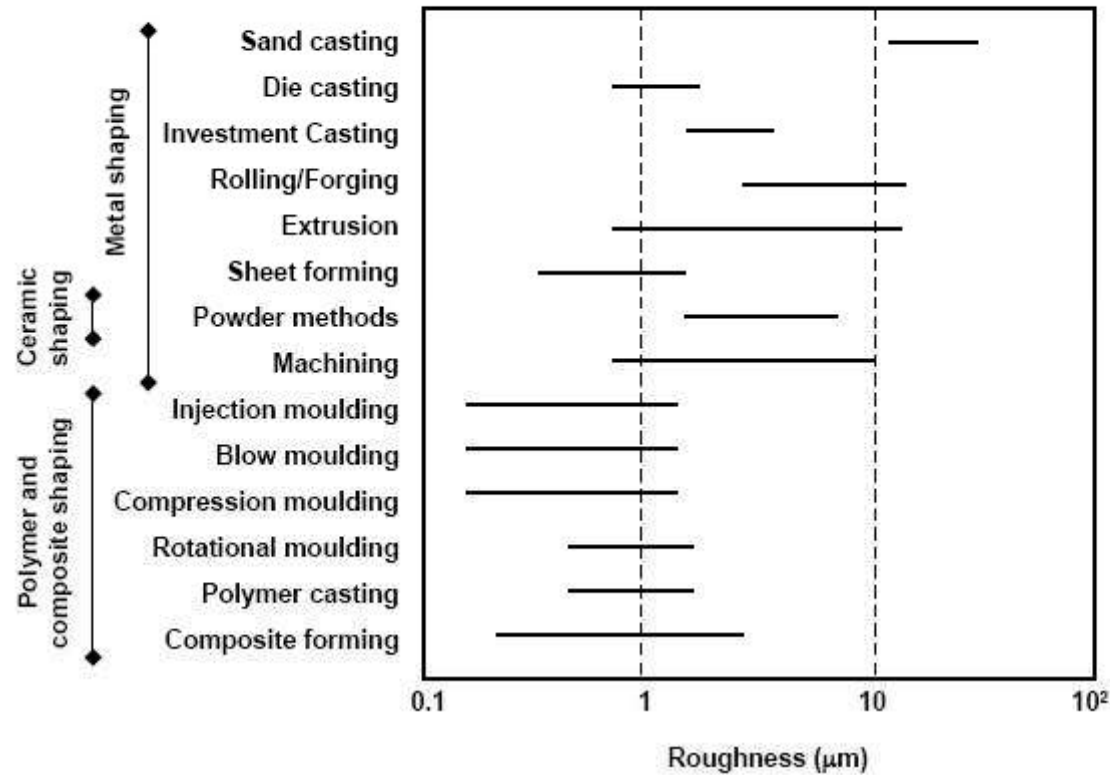



MALZEMELERİN PROSES ÖZELLİK KARTLARI-5- (Boyut toleransı)

IV.5 DIMENSIONAL TOLERANCE

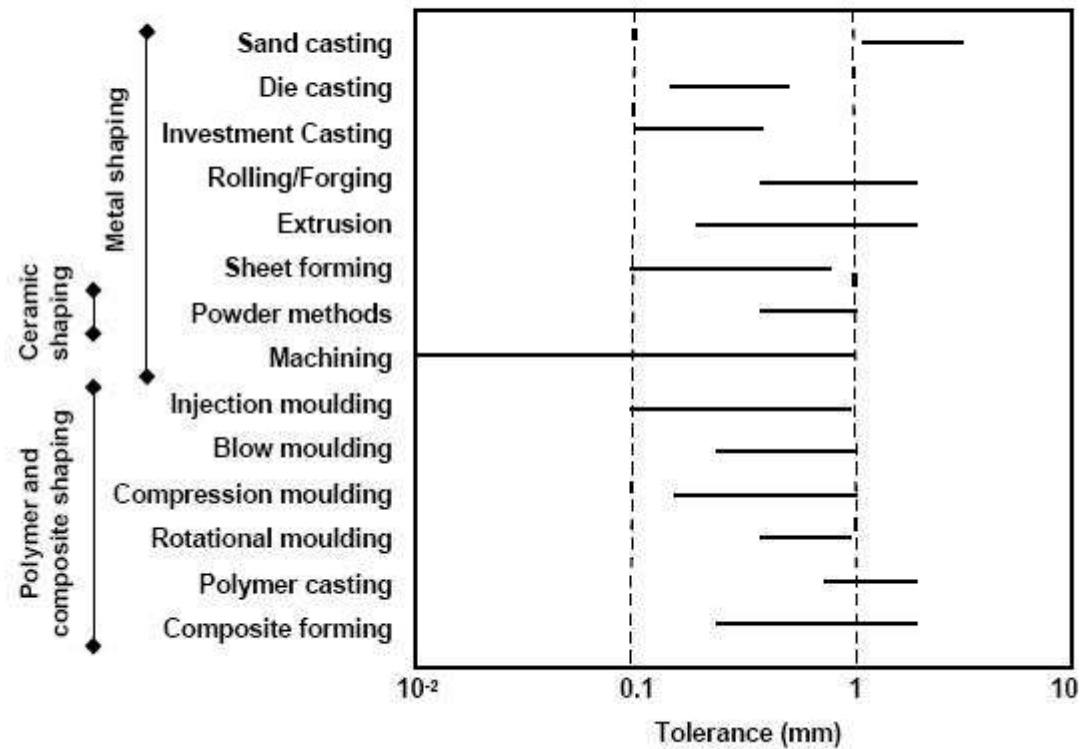




MALZEMELERİN PROSES ÖZELLİK KARTLARI-6- (Ekonomik parça büyüklüğü)



IV.6 ECONOMIC BATCH SIZE

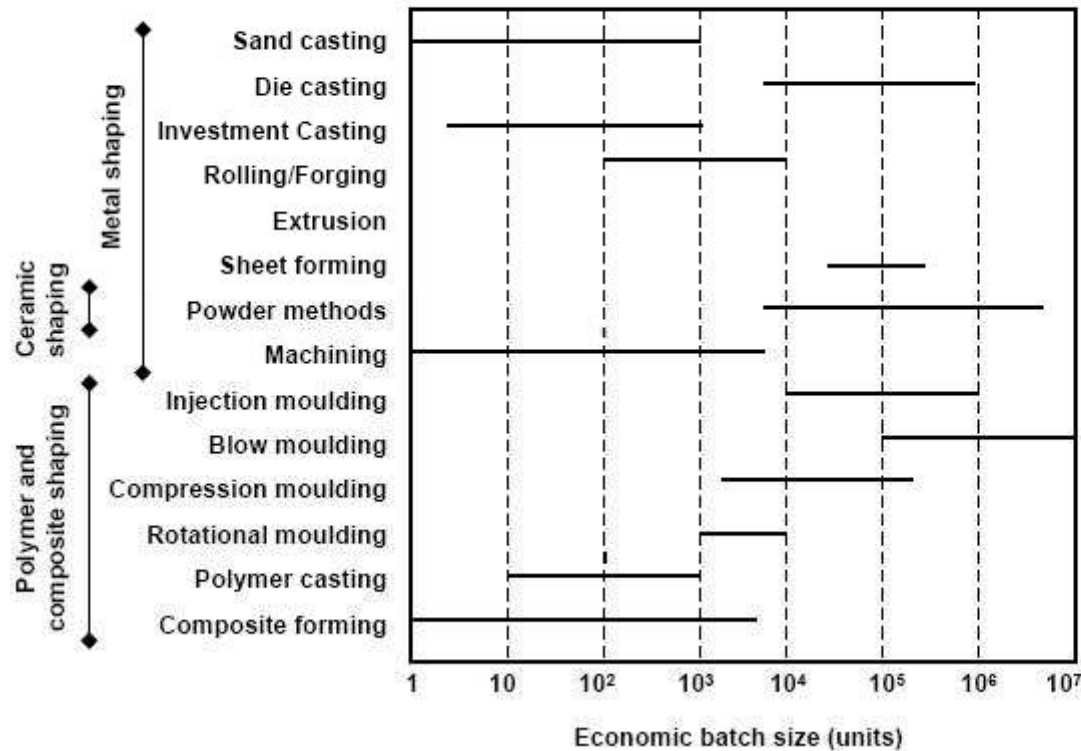



METALLERİN KULLANIM YERLERİ



V. CLASSIFICATION AND APPLICATIONS OF ENGINEERING MATERIALS

V.1 METALS: FERROUS ALLOYS, NON-FERROUS ALLOYS

Metals		Applications
Ferrous	Cast Irons	Automotive parts, engine blocks, machine tool structural parts, lathe beds
	High Carbon Steels	Cutting tools, springs, bearings, cranks, shafts, railway track
	Medium Carbon Steels	General mechanical engineering (tools, bearings, gears, shafts, bearings)
	Low Carbon Steels	Steel structures ("mild steel") – bridges, oil rigs, ships; reinforcement for concrete; automotive parts, car body panels; galvanised sheet; packaging (cans, drums)
	Low Alloy Steels	Springs, tools, ball bearings, automotive parts (gears connecting rods etc)
	Stainless Steels	Transport, chemical and food processing plant, nuclear plant, domestic ware (cutlery, washing machines, stoves), surgical implements, pipes, pressure vessels, liquid gas containers
Non-ferrous	Aluminium Alloys	
	Casting Alloys	Automotive parts (cylinder blocks), domestic appliances (irons)
	Non-heat-treatable Alloys	Electrical conductors, heat exchangers, foil, tubes, saucepans, beverage cans, lightweight ships, architectural panels
	Heat-treatable Alloys	Aerospace engineering, automotive bodies and panels, lightweight structures and ships
	Copper Alloys	Electrical conductors and wire, electronic circuit boards, heat exchangers, boilers, cookware, coinage, sculptures
	Lead Alloys	Roof and wall cladding, solder, X-ray shielding, battery electrodes
	Magnesium Alloys	Automotive castings, wheels, general lightweight castings for transport, nuclear fuel containers; principal alloying addition to Aluminium Alloys
	Nickel Alloys	Gas turbines and jet engines, thermocouples, coinage; alloying addition to austenitic stainless steels
	Titanium Alloys	Aircraft turbine blades; general structural aerospace applications; biomedical implants.
Zinc Alloys	Die castings (automotive, domestic appliances, toys, handles); coating on galvanised steel	





POLİMERLERİN VE KÖPÜKLERİN KULLANIM YERLERİ



V.2 POLYMERS AND FOAMS

Polymers		Abbreviation	Applications
Elastomer	Butyl Rubber		Tyres, seals, anti-vibration mountings, electrical insulation, tubing
	Ethylene-vinyl-acetate	EVA	Bags, films, packaging, gloves, insulation, running shoes
	Isoprene	IR	Tyres, inner tubes, insulation, tubing, shoes
	Natural Rubber	NR	Gloves, tyres, electrical insulation, tubing
	Polychloroprene (Neoprene)	CR	Wetsuits, O-rings and seals, footwear
	Polyurethane Elastomers	el-PU	Packaging, hoses, adhesives, fabric coating
	Silicone Elastomers		Electrical insulation, electronic encapsulation, medical implants
Thermoplastic	Acrylonitrile butadiene styrene	ABS	Communication appliances, automotive interiors, luggage, toys, boats
	Cellulose Polymers	CA	Tool and cutlery handles, decorative trim, pens
	Ionomer	I	Packaging, golf balls, blister packs, bottles
	Polyamides (Nylons)	PA	Gears, bearings; plumbing, packaging, bottles, fabrics, textiles, ropes
	Polycarbonate	PC	Safety goggles, shields, helmets; light fittings, medical components
	Polyetheretherketone	PEEK	Electrical connectors, racing car parts, fibre composites
	Polyethylene	PE	Packaging, bags, squeeze tubes, toys, artificial joints
	Polyethylene terephthalate	PET	Blow moulded bottles, film, audio/video tape, sails
	Polymethyl methacrylate (Acrylic)	PMMA	Aircraft windows, lenses, reflectors, lights, compact discs
	Polyoxymethylene (Acetal)	POM	Zips, domestic and appliance parts, handles
	Polypropylene	PP	Ropes, garden furniture, pipes, kettles, electrical insulation, astroturf
	Polystyrene	PS	Toys, packaging, cutlery, audio cassette/CD cases
	Polyurethane Thermoplastics	tp-PU	Cushioning, seating, shoe soles, hoses, car bumpers, insulation
Polyvinylchloride	PVC	Pipes, gutters, window frames, packaging	
Polytetrafluoroethylene (Teflon)	PTFE	Non-stick coatings, bearings, skis, electrical insulation, tape	
Thermoset	Epoxies		Adhesives, fibre composites, electronic encapsulation
	Phenolics		Electrical plugs, sockets, cookware, handles, adhesives
	Polyester		Furniture, boats, sports goods
Polymer Foams	Flexible Polymer Foam		Packaging, buoyancy, cushioning, sponges, sleeping mats
	Rigid Polymer Foam		Thermal insulation, sandwich panels, packaging, buoyancy





KOMPOZİTLERİN, SERAMİKLERİN, CAMLARIN VE NATURAL MALZEMELERİN KULLANIM YERLERİ

V.3 COMPOSITES, CERAMICS, GLASSES AND NATURAL MATERIALS

Composites		Applications
Metal	Aluminium/Silicon Carbide	Automotive parts, sports goods
Polymer	CFRP GFRP	Lightweight structural parts (aerospace, bike frames, sports goods, boat hulls and oars, springs) Boat hulls, automotive parts, chemical plant
Ceramics		
Glasses	Borosilicate Glass Glass Ceramic Silica Glass Soda-Lime Glass	Ovenware, laboratory ware, headlights Cookware, lasers, telescope mirrors High performance windows, crucibles, high temperature applications Windows, bottles, tubing, light bulbs, pottery glazes
Porous	Brick Concrete Stone	Buildings General civil engineering construction Buildings, architecture, sculpture
Technical	Alumina Aluminium Nitride Boron Carbide Silicon Silicon Carbide Silicon Nitride Tungsten Carbide	Cutting tools, spark plugs, microcircuit substrates, valves Microcircuit substrates and heatsinks Lightweight armour, nozzles, dies, precision tool parts Microcircuits, semiconductors, precision instruments, IR windows, MEMS High temperature equipment, abrasive polishing grits, bearings, armour Bearings, cutting tools, dies, engine parts Cutting tools, drills, abrasives
Natural		
	Bamboo Cork Leather Wood	Building, scaffolding, paper, ropes, baskets, furniture Corks and bungs, seals, floats, packaging, flooring Shoes, clothing, bags, drive-belts Construction, flooring, doors, furniture, packaging, sports goods





ELEMENTLERİN ATOMİK ÖZELLİKLERİ



VIII. PHYSICAL PROPERTIES OF SELECTED ELEMENTS

ATOMIC PROPERTIES OF SELECTED ELEMENTS

Element	Symbol	Atomic Number	Relative Atomic Weight ¹	Melting Point (°C)	Crystal structure ² (at 20°C)	Lattice constants ³ (at 20°C)	
						a, b) (Å)	c (Å)
Aluminium	Al	13	26.982	660	f.c.c.	4.0496	
Beryllium	Be	4	9.012	1280	h.c.p.	2.2856	3.5843
Boron	B	5	10.811	2300	t.	6.73	5.03
Carbon	C	6	12.011	3500	hex.	2.4612	6.7079
Chlorine	Cl	17	35.453	-101	-	-	-
Chromium	Cr	24	51.996	1900	b.c.c.	2.8850	
Copper	Cu	29	63.54	1083	f.c.c.	2.5053	
Germanium	Ge	32	72.59	958	d.	5.6575	
Gold	Au	79	196.967	1063	f.c.c.	4.0786	
Hydrogen	H	1	1.008	-259	-	-	-
Iron	Fe	26	55.847	1534	b.c.c.	2.8663	
Lead	Pb	82	207.19	327	f.c.c.	4.9505	
Magnesium	Mg	12	24.312	650	h.c.p.	3.2094	5.2103
Manganese	Mn	25	54.938	1250	cub.	6.912	
Molybdenum	Mo	42	95.94	2620	b.c.c.	3.1466	
Nickel	Ni	28	58.71	1453	f.c.c.	3.5241	
Niobium	Nb	41	92.906	2420	b.c.c.	3.3007	
Nitrogen	N	7	14.007	-210	-	-	-
Oxygen	O	8	15.999	-219	-	-	-
Phosphorus	P	15	30.974	44	cub.	7.17 (at -35°C)	
Silicon	Si	14	28.086	1414	d.	5.4305	
Silver	Ag	47	107.870	961	f.c.c.	4.0862	
Sulphur	S	16	32.064	119	f.c.orth.	10.437, (12.845)	24.369
Tin	Sn	50	118.69	232	b.c.t.	5.6313	3.1612
Titanium	Ti	22	47.90	1670	h.c.p.	2.9504	4.6633
Tungsten	W	74	183.85	3380	b.c.c.	3.1652	
Vanadium	V	23	50.942	1920	b.c.c.	3.0282	
Zinc	Zn	30	65.37	419	h.c.p.	2.6649	4.9468
Zirconium	Zr	40	91.22	1850	h.c.p.	3.2312	5.1475

¹ The values of atomic weight are those in the Report of the International Commission on Atomic Weights (1961). The unit is $1/12^{\text{th}}$ of the mass of an atom of C^{12} .

² f.c.c. = face-centred cubic; h.c.p. = hexagonal close-packed; b.c.c. = body-centred cubic; t. = tetragonal; hex. = hexagonal; d. = diamond structure; cub. = cubic; f.c.orth. = face-centred orthorhombic; b.c.t. = body-centred tetragonal.

³ Lattice constants are in Ångström units ($1 \text{ Å} = 10^{-10} \text{ m}$)





ELEMETLERİN OKSİTLENME ÖZELLİKLERİ

OXIDATION PROPERTIES OF SELECTED ELEMENTS

Standard electrode potentials (300K, molar solutions)

Oxidation reaction for solution of the metal	Normal hydrogen scale (volts)
$Mg \rightarrow Mg^{2+} + 2e^{-}$	- 2.36
$Al \rightarrow Al^{3+} + 3e^{-}$	- 1.66
$Zn \rightarrow Zn^{2+} + 2e^{-}$	- 0.76
$Cr \rightarrow Cr^{3+} + 3e^{-}$	- 0.74
$Fe \rightarrow Fe^{2+} + 2e^{-}$	- 0.44
$Ni \rightarrow Ni^{2+} + 2e^{-}$	- 0.25
$Sn \rightarrow Sn^{2+} + 2e^{-}$	- 0.14
$Pb \rightarrow Pb^{2+} + 2e^{-}$	- 0.13
$H_2 \rightarrow 2H^{+} + 2e^{-}$	0.00
$Sn^{2+} \rightarrow Sn^{4+} + 2e^{-}$	+ 0.15
$Cu \rightarrow Cu^{2+} + 2e^{-}$	+ 0.34
$O_2 + 2H_2O + 4e^{-} \rightarrow 4(OH)^{-}$	+ 0.40
$Fe^{2+} \rightarrow Fe^{3+} + e^{-}$	+ 0.77
$Ag \rightarrow Ag^{+} + e^{-}$	+ 0.80
$2H_2O \rightarrow O_2 + 4H^{+} + 4e^{-}$	+ 1.23
$Au \rightarrow Au^{3+} + 3e^{-}$	+ 1.42

Free energy of oxidation (at 273K)

Material	Oxide	Free energy (kJ/mol O ₂)
Beryllium	BeO	- 1182
Magnesium	MgO	- 1162
Aluminium	Al ₂ O ₃	- 1045
Zirconium	ZrO ₂	-1028
Titanium	TiO	- 848
Silicon	SiO ₂	- 836
Niobium	Nb ₂ O ₅	- 757
Chromium	Cr ₂ O ₃	- 701
Zinc	ZnO	- 636
Silicon nitride	3SiO ₂ + 2N ₂	- 629
Silicon carbide	SiO ₂ + CO ₂	- 580
Molybdenum	MoO ₂	- 534
Tungsten	WO ₃	- 510
Iron	Fe ₃ O ₄	- 508
Nickel	NiO	- 439
Most polymers	-	- 400
Diamond, graphite	CO ₂	- 389
Lead	Pb ₃ O ₄	- 309
Copper	CuO	- 254
GFRP	-	- 200
Silver	Ag ₂ O	- 5
Gold	Au ₂ O ₃	+ 80

(Data courtesy of Granta Design Ltd)





BİRİMLERİN BİRBİRLERİNE DÖNÜŞÜMÜ

CONVERSION OF UNITS – STRESS, PRESSURE AND ELASTIC MODULUS *

	MN/m ² (or MPa)	lb/in ²	kgf/mm ²	bar
MN/m ² (or MPa)	1	1.45×10^2	0.102	10
lb/in ²	6.89×10^{-3}	1	7.03×10^{-4}	6.89×10^{-2}
kgf/mm ²	9.81	1.42×10^3	1	98.1
bar	0.10	14.48	1.02×10^{-2}	1

CONVERSION OF UNITS – ENERGY *

	J	cal	eV	ft lbf
J	1	0.239	6.24×10^{18}	0.738
cal	4.19	1	2.61×10^{19}	3.09
eV	1.60×10^{-19}	3.83×10^{-20}	1	1.18×10^{-19}
ft lbf	1.36	0.324	8.46×10^{18}	1

CONVERSION OF UNITS – POWER *

	kW (kJ/s)	hp	ft lbf/s
kW (kJ/s)	1	1.34	7.38×10^2
hp	0.746	1	5.50×10^2
ft lbf/s	1.36×10^{-3}	1.82×10^{-3}	1





BALIKESİR ÜNİVERSİTESİ

Doç.Dr. İrfan AY / Arş.Gör. T.Kerem DEMİRCİOĞLU



BALIKESİR



ÜNİVERSİTESİ



Doç. Dr. İRFAN AY / Arş. Gör. T.KEREM DEMİRCİOĞLU